

Insights on the surface chemistry of BiVO₄ photoelectrodes and the role of Al overlayers on its water oxidation activity

Kristine Tolod, Tapish Saboo, Simelys Hernandez, Hilmar Guzman, Micaela Castellino, Rowshanak Irani, Peter Bogdanoff, Fatwa F. Abdi, Elsje Alessandra Quadrelli, Nunzio Russo

► To cite this version:

Kristine Tolod, Tapish Saboo, Simelys Hernandez, Hilmar Guzman, Micaela Castellino, et al.. Insights on the surface chemistry of BiVO₄ photoelectrodes and the role of Al overlayers on its water oxidation activity. *Applied Catalysis A: General*, Elsevier, 2020, 605, pp.117796. 10.1016/j.apcata.2020.117796 . hal-03058539

HAL Id: hal-03058539

<https://hal.archives-ouvertes.fr/hal-03058539>

Submitted on 11 Dec 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Insights on the surface chemistry of BiVO₄ photoelectrodes and the role of Al overlayers on its water oxidation activity

Kristine Rodulfo Tolod,^{1,2*} Tapish Saboo,² Simelys Hernández,^{1*} Hilmar Guzmán,^{1,3} Micaela Castellino,¹ Rowshanak Irani,⁴ Peter Bogdanoff,⁴ Fatwa F. Abdi,⁴ Elsje Alessandra Quadrelli² and Nunzio Russo¹

¹Department of Applied Science and Technology, Politecnico di Torino, Corso Duca degli Abruzzi, 10129 Turin, Italy

²Université de Lyon, Institut de Chimie de Lyon, UMR 5265 – CNRS – Université Lyon 1, ESCPE Lyon, Laboratoire de Chimie, Catalyse, Polymères et Procédés (C₂P₂), Equipe Chimie Organométallique de Surface, 43, Bd du 11 Novembre 1918, F-69616 Villeurbanne, France

³Center for Sustainable Future Technologies, Istituto Italiano di Tecnologia @ Polito, Via Livorno, 60, 10144, Turin, Italy.

⁴Institute for Solar Fuels, Helmholtz-Zentrum Berlin für Materialien und Energie, Berlin 14109, Germany

*E-mails of corresponding authors: kristine.tolod@polito.it, simelys.hernandez@polito.it

Abstract

Bismuth vanadate (BiVO₄) have surface states that give rise to defect levels that mediate electron-hole recombination. In order to minimize the inefficiencies, an ultrathin Al overlayer was deposited on the BiVO₄ electrodes. A 54% improvement on the photocurrent density was obtained using the Al- modified BiVO₄ electrode, accompanied by a 15% increase in stability over 7.5 hours of continuous irradiation. Moreover, surface capacitance measurements showed that the Al overlayer was indeed passivating the surface states. We also shed light on the deposition of an Al overlayer on the surface of BiVO₄, by investigating the process on model BiVO₄ powders. This study presents useful, previously unreported information about the surface chemistry of BiVO₄ based on experimental methods and gives unique insights on the characterization of the BiVO₄ surface. The existence of surface reactive sites on BiVO₄ was confirmed and quantified (1.5 reactive sites/nm²) via chemical titration.

Keywords: BiVO₄, Al overlayer, passivation layer, photoanode, surface chemistry, water splitting, artificial photosynthesis, surface organometallic chemistry

1. Introduction

Photoelectrochemical water splitting is a sustainable means to produce H_2 , which can serve as a clean source of fuel. In this process, liquid water is split into its gaseous H_2 and O_2 components ($H_2O + \text{photons} \rightarrow H_2 + \frac{1}{2} O_2$), via the use of photo-activated semiconductor catalysts, by utilizing the photons coming from the sun and using them to directly convert the solar energy into chemical energy. To be able to split water into hydrogen and oxygen efficiently and sustainably, the photo-voltage must be sufficient, there should be an appropriate band alignment in the semiconductor, a substantial absorption of the solar spectrum and an efficient and fast transport of charges between the semiconductor and the electrolyte [1,2]. In addition, the semiconductor must be stable and cost-effective. The search for suitable materials that satisfy these requirements is the focus of the current on-going studies in photoelectrochemistry and photocatalysis because no single material can fulfil all these requirements; trade-offs exist among the light-harvesting ability, the charge transport and charge transfer processes, and the catalyst's influence in the kinetics of the reaction.

The bottleneck in the photoelectrochemical water splitting process is the water oxidation reaction in the photoanode [3,4], which is the focus of this study. Metal oxides [5,6] are preferred as photoanodes, mainly because of their resistance to oxidizing conditions [2]. Compared to other metal oxides like hematite ($\alpha\text{-Fe}_2\text{O}_3$) and WO_3 , bismuth vanadate ($BiVO_4$) is preferred because its conduction band edge position nearly coincides with the thermodynamic hydrogen evolution potential [7,8], which is instrumental in promoting an earlier photocurrent onset and enabling the generation of higher photocurrents in the low bias region [9]. It also has a relatively low band gap energy (2.4-2.5 eV), which makes it readily absorb visible light [10,11]. The theoretical maximum photocurrent density of $BiVO_4$ is 7.5 mA/cm^2 , which translates to a maximum of 9% of solar-to-hydrogen (STH) efficiency [12,13] assuming all of the sunlight photons with energies greater than 2.4 eV are absorbed by the semiconductor and have contributed to the photocurrent.

However, solid semiconductors such as $BiVO_4$ have surface states that are associated with the abrupt termination and discontinuity of the solid crystal at the crystal boundary. As a result, the electronic band structure is quite different from the bulk, as characterized by dangling bonds [14]. These surface states have a modified band structure that may give rise to defect energy levels, which may lie within the previously forbidden band gap region away from the band edges. These can mediate electron-hole recombination via the Shockley-Read-Hall mechanism wherein the electron from the conduction band can move towards the defect level, release the energy as photon or phonons, and eventually relax into the valence band, annihilating a hole in the process.

In photoelectrochemical systems, passivation layers have been used as an effective strategy to improve the charge separation and transfer processes across semiconductor–liquid interfaces. These thin layers can reduce the charge recombination at surface states, increase the water oxidation reaction kinetics, and protect the semiconductor from chemical corrosion. These layers are <100 nm thick but quite often, only 1–2 nm are used to allow the charge transfer by means of tunneling. Passivation layers can be fabricated through the use of several relatively scalable techniques such as atomic layer deposition (ALD), spin-coating, electrochemical deposition, sputtering, electron beam evaporation, floating transfer and dip-casting [15–17].

Al_2O_3 has been used as a passivation layer for both p- and n-type silicon solar cells. Al_2O_3 is a wide band gap material (5-9 eV) which exists in different crystalline forms, exhibits low leakage current, and has a modest value of dielectric constant [18]. It finds its use as a gate dielectric in metal oxide semiconductor (MOS) transistors and is a suitable insulator for various electronic applications. In the photovoltaic field, the importance and crucial impact of surface recombination to the resulting photoactivity of conventional semiconductors has been very much highlighted. Al_2O_3 as a passivation layer is unique because it combines the effect of both chemical and field effect passivation by providing hydrogen to the Si interface during the post-deposition thermal treatments and also for having a very high density of negative charges located near the interface [19]. However, the use of Al_2O_3 as a passivation layer for $BiVO_4$ photoanodes has not been largely investigated. To date, only one paper reported the use of Al_2O_3 as a passivation layer for $BiVO_4$ [20]. It was shown that adding an Al overlayer with an optimal thickness can double the photocurrent density, however, the nature of the specific surface interactions between the Al overlayer and the $BiVO_4$ remains to be studied.

This study presents novel findings about the use of ultrathin overlayers of Al to enhance the photoactivity of BiVO₄. Moreover, an organometallic chemistry approach was used to study this very important surface as well as to introduce surface modifications that could help improve the photoactivity and the stability of this material.

2. Experimental

2.1 Materials and Methods

2.1.1 *Synthesis Procedures*

A full description of materials and methods used for the synthesis of both BiVO₄ powders and films is reported in the Supporting Information (SI, sections S1 and S2). Briefly, the BiVO₄ powder was synthesised by hydrothermal method employing a solution of bismuth nitrate and ammonium metavanadate as precursors, under acidic media (pH=0), in an autoclave at 180°C for 12h, according to a previous published procedure [21]. The crystalline BiVO₄ powder was obtained after calcination under air atmosphere at 400 °C for 2h. The BiVO₄ films were synthesised based on a previously optimized electrodeposition method [22]. In brief, BiOI was electrodeposited on F-doped Tin oxide (FTO)/glass substrate by using a solution of bismuth nitrate, potassium iodide, p-benzoquinone and ethanol. The BiOI film was subsequently transformed in BiVO₄ by addition of a solution of vanadyl acetylacetonate in dimethyl sulfoxide and calcination under air atmosphere at 425 °C for 2h. The photoelectrode area is of 1 cm². The BiVO₄ powders and thin films were modified by the addition of Al₂O₃ with the procedure described in the SI (sections S1.4 and S2.3, respectively). In particular, the BiVO₄ films with different amounts (or cycles) of deposited Al₂O₃ were investigated.

2.1.2 *Materials Characterization*

A Merlin Zeiss Field Emission – Scanning Electron Microscope (FESEM) equipped with an Energy Dispersive X-ray Spectroscopy System (EDS) was used to study the morphology of the samples. The XRD spectra were obtained by using an X'Pert Phillips diffractometer under Cu K α radiation (λ = 1.5418 Å) set at 40 kV and 40 mA. N₂ adsorption and desorption isotherms were obtained at 77K on a degassed sample using Belsorp-Max from BEL-JAPAN. The DRIFTS spectra were obtained using a Nicolet 6700-FT spectrometer. Gas chromatography (GC) measurements were determined using a HP 5890 gas chromatograph equipped with a flame ionization detector (FID) and a KCl/Al₂O₃ on fused silica column (50 m x 0.32 mm). UV-Vis absorption spectra of BiVO₄ films were measured using a Perkin-Elmer Lambda 950 double-beam spectrometer equipped with an integrating sphere. X-ray photoelectron spectroscopy (XPS) measurements were performed with a monochromatic Al K α radiation (h ν = 1486.74 eV), in order to determine the surface composition of the BiVO₄ electrodes and their stability after the photoelectrochemical tests. Bare BiVO₄ samples were first analysed by using a PHI 5000 Versa Probe (Physical Electronics) system. Subsequently, a SPECS FOCUS 500 monochromator and a hemispherical electron analyzer (SPECS PHOIBOS 100) were employed to further analyse the bare and Al-modified BiVO₄ samples before and after testing. The binding energies for all spectra were calibrated with respect to the adventitious carbon C 1s peak at 284.5 eV. Peak fitting was done using XPSPEAK software with a Shirley background subtraction.

2.1.3 *Photoelectrochemical (PEC) Characterization*

A Pt coil counter electrode (CE), an Ag/AgCl (3M KCl) reference electrode (RE), and the BiVO₄ photoanode as the working electrode (WE), were assembled in a single-compartment quartz cell containing a 0.1 M NaPi solution (pH 7). The simulated sunlight irradiation was from a Newport 450 W Xe lamp source that was equipped with an AM 1.5G filter (intensity of 100 mW/cm²). Illumination was performed under back illumination on a geometric area of 1 cm², which corresponds to the entire deposited area of the electrode.

The PEC tests were performed using a BioLogic VSP 300 potentiostat. Linear sweep voltammetry (LSV) in continuous and chopped light modes and chronoamperometry (CA) were performed to characterize the photoactivity of the electrodes. Linear sweep voltammetry was performed at the potential range of -0.3 V to 1 V vs. Ag/AgCl, using a scan rate of 10 mV/s. Chronoamperometry was done at 0.61V vs. Ag/AgCl. The following Nernst equation was used to convert the potentials versus the Ag/AgCl (3M KCl) reference electrode to RHE (NHE at pH=0):

$$E_{RHE} = E_{\frac{Ag}{AgCl}} + 0.059pH + E_{\frac{Ag}{AgCl}}^o \left(E_{\frac{Ag}{AgCl}}^o = +0.199 V \right) \quad (1)$$

MS-SPEIS (Mott Schottky-Staircase Potentio Electrochemical Impedance Spectroscopy) analysis was done under an applied potential of -0.8 V to 1 V (vs. Ag/AgCl), and a frequency of 7.5 kHz. Mott-Schottky plots were used to extrapolate the flat band potentials (E_{fb}) and donor densities (N_D) of the photoanodes, according to the equation:

$$\frac{1}{C^2} = \frac{2}{\epsilon\epsilon_0 A^2 e N_D} \left(E - E_{fb} - \frac{k_B T}{e} \right) \quad (2)$$

where C is the interfacial capacitance, ϵ is the dielectric constant of the semiconductor, ϵ_0 is the permittivity of free space, A is the area of the interfacial capacitance, N_D is the donor density, E is the applied potential, E_{fb} is the flat-band potential, k_B is the Boltzmann's constant, T is the temperature and e is the electronic charge. A plot of $\frac{1}{C^2} A^2$ versus the potential yields a linear region.

Charge transport and transfer properties of the photoanodes were studied using electrochemical impedance spectroscopy (EIS), at frequencies from 0.1 Hz to 0.5 MHz, a potential of 0.61 V vs. Ag/AgCl, under simulated sunlight illumination.

Monochromatic photocurrents (i_{ph}) of $BiVO_4$ films were measured under the illumination of a Xe lamp source (Oriel, 300 W) coupled with a grating monochromator (Acton SpectraPro 150i). A long-pass filter (Schott, 3 mm thick) was placed between the monochromator and the sample in order to remove any second-order diffracted light. The optical power of lights reaching the films (P) was measured using a calibrated photodiode (Ophir, PD300R-UV with Nova II controller). An EG&G Princeton Applied Research 283 potentiostat was used to apply the bias potential. An Ag/AgCl (saturated KCl, XR300 Radiometer Analytical) and a platinum wire were used as the reference and counter electrode, respectively. Incident photon-to-current conversion efficiency (IPCE) values for each wavelength (λ) were calculated using the following formula:

$$IPCE(\lambda) = \frac{1240 \times i_{ph}(mA)}{P(mW) \times \lambda(nm)} \times 100\% \quad (3)$$

For O_2 detection, differential electrochemical mass spectrometry measurements were performed using a setup described in details elsewhere [23,24]. Signal calibration was performed by measuring the O_2 signal vs. current for a Pt sheet. The Faradaic efficiency (FE) was then calculated using the following equation, under the assumption that the Pt sheet has 100% Faradaic efficiency for the O_2 evolution reaction:

$$FE = \frac{O_2 \text{ signal from sample}}{O_2 \text{ signal from Pt sheet}} \quad (4)$$

Finally, rapid scan voltammetry was performed. A constant potential of 1.5 V vs Ag/AgCl (2.1 V vs RHE) was applied for 2 minutes as a conditioning step, followed by a quick potential sweep to -0.2 V vs Ag/AgCl (0.4 V vs RHE) with a scan rate of 1 V/s. Comparison of the curves with and without conditioning yields the surface capacitance (C) through the equation $C = (J_{\text{with cond}} - J_{\text{w/out cond}}) / \text{scan rate}$.

3 Results and Discussions

3.1 Morphology and Structure

$BiVO_4$ has three main crystal forms: monoclinic scheelite, tetragonal zircon-type and tetragonal scheelite. There is an irreversible transition from the tetragonal zircon-type to the monoclinic scheelite structure that occurs at 400–500 °C. At 255°C, another reversible transition also occurs between the monoclinic-scheelite and the tetragonal scheelite structures. Furthermore, mechanical grinding at room temperature can also irreversibly transform the tetragonal structure into a monoclinic structure [25]. Among these three crystal structures, the monoclinic scheelite structure is the most commonly used for photocatalysis because of its higher photoactivity compared to the other structures [26]. We prepared two different form of samples: $BiVO_4$ powders that were synthesized hydrothermally and $BiVO_4$ thin-film

electrodes prepared via electrodeposition. The reader is referred to the Supporting Information (S1 and S2) for the detailed synthesis procedures. The XRD spectra in **Erreur ! Source du renvoi introuvable.** showed that both the BiVO₄ electrode and the BiVO₄ powder manifested the monoclinic scheelite structure (JCPDS No. 14-0688, space group: I2/a, a=5.195, b=11.701, c=5.092, $\beta=90.38^\circ$), which is evident from the peak splitting at the 2 θ values of 18.5° and 35°. No traces of other phases were observed in these diffraction patterns, which points out the suitability of the chosen synthesis methods towards the monoclinic phase of BiVO₄. For an easy comparison, the XRD reference spectra of BiVO₄ with monoclinic scheelite and tetragonal zircon-type structures are also shown in the Figure 1.

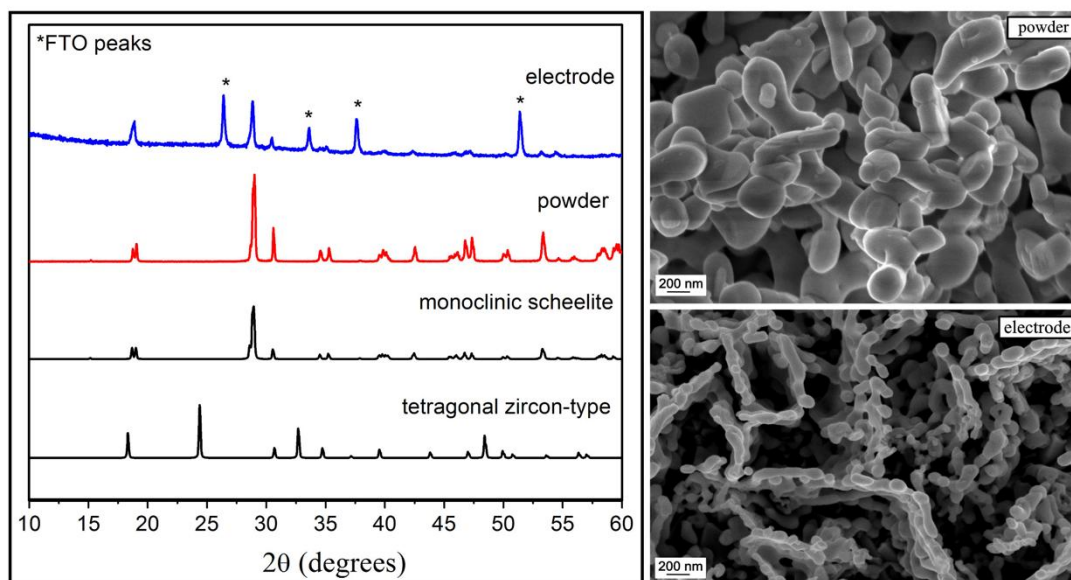


Figure 1. XRD (left) and FESEM (right) images of bare BiVO₄ powder and thin-film electrode. The reference XRD spectra of monoclinic scheelite and tetragonal zircon-type structures of BiVO₄ are shown for comparison in the bottom of the left image.

From the FESEM images in Figure 1, it is evident that there were very distinct differences between the resulting morphologies of the BiVO₄ powder and the thin-film electrode. The BiVO₄ powder morphology consists of a more agglomerated and compact structure that is made up of big grain sizes, while the thin film electrode showed a more porous structure that is not agglomerated, and with smaller grains. In agreement with this, the crystallite sizes for the powder and the thin film electrode, which were determined from the X-ray diffraction data, are found to be 320 and 112 nm, respectively. More intense peaks were observed from the powder samples because of the higher amount of material present than in the thin-film electrode. From FESEM-EDS, the ratio of Bi/V for each of the samples was both found to be 1, which means that the 1:1 ratio of Bi: V is well-maintained in the bulk for both samples. Nitrogen adsorption-desorption isotherms were used for the BET surface area measurements for the BiVO₄ powder, which revealed a rather low surface area of 2-4 m²/g.

3.2 BiVO₄ powder

The nature of the BiVO₄ surface was studied by the chemical titration of the BiVO₄ powder with n-butyllithium (n-BuLi), a carbanionic reagent, typically used in surface organometallic chemistry for the titration of surface acid protons (see SI, section S1.3, for more details). The n-BuLi is known to react with the surface hydroxyls and chemisorbed water of inorganic oxides[27] to yield butane (C₄H₁₀) that can be quantified using a gas chromatograph (GC).

From the n-BuLi reaction, 8.8 μ mol of butane gas (C₄H₁₀) was evolved when contacted with the thermally-treated, dehydroxylated BiVO₄. If one extrapolated such chemical reaction to exclusive reaction with surface reactive sites, the result translates to 1.5 surface reactive sites/nm² on the BiVO₄ surface. The

reader is referred to the SI (section S3) for the gas chromatography calculations. In a study by Starr et. al. [28], it was shown that single crystal BiVO_4 exhibited the presence of surface hydroxyl groups, however, there is no evidence in literature that confirms their presence in polycrystalline structures such as BiVO_4 powders.

The IR spectra of the pristine BiVO_4 powder (black line) and the titrated BiVO_4 powder (red line) in the 500 to 2000 cm^{-1} region is shown in Figure 2. The BiVO_4 powder titrated with $n\text{-BuLi}$ showed two distinct IR bands in the 1098.5 cm^{-1} and 1259 cm^{-1} regions. This preliminary data necessitates further studies to characterize the surface chemical species and to see if hydroxyl to O-Li^+ titration with concomitant alkane stoichiometric release is the dominant surface reactivity. As of now, the 1.5 OH/nm^2 can be considered as an upper boundary estimate of the hydroxyl population on the BiVO_4 surface. To the best of our knowledge, this quantification of the OH groups in BiVO_4 surface has not been previously reported in literature.


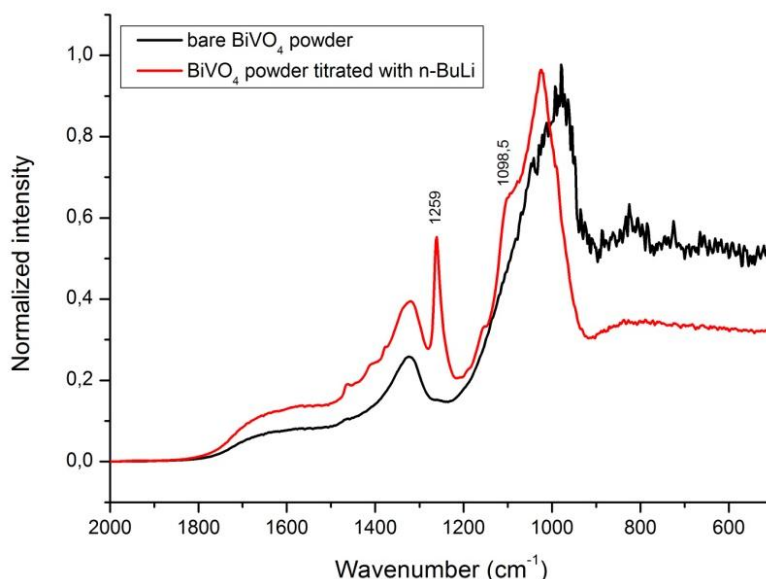


Figure 2. FTIR spectra of bare BiVO_4 and BiVO_4 titrated with $n\text{-BuLi}$

The addition of an Al overlayer was also performed on BiVO_4 powder in order to model the $\text{BiVO}_4\text{-Al}$ interface formed on the photoanode. Such modeling on the powder's surface, which has a 10^4 -fold larger surface area than that of the thin film electrode (ca. 2 m^2/g for powder vs. few cm^2/g for the electrode), allows to use millimolar range routine characterization techniques (such as DRIFT IR, elemental analysis by combustion, GC analysis of the gas phase), thus, giving molecular-level insight to the surface processes, which would be more difficult to harness directly from the electrode surface [29].

The accepted simplified ALD-mechanism for Al_2O_3 growth on OH-terminated surfaces is shown below, with * denoting the surface species [30].



When the reaction is performed in a sequential manner, i.e. A-B-A-B-A-B..., a controlled layer-by-layer growth of Al_2O_3 is achieved. However, to the best of our knowledge, the mechanism of the growth of an Al overlayer on BiVO_4 has not been investigated to date. We have earlier established and quantified the presence of reactive sites on the BiVO_4 surface, and we have hypothesized that some OH groups can serve as initial binding sites for the Al atoms as indicated in sequence A. Consequently, the growth of the Al overlayer in an A-B-A-B-A-B sequential manner should also be possible for BiVO_4 .

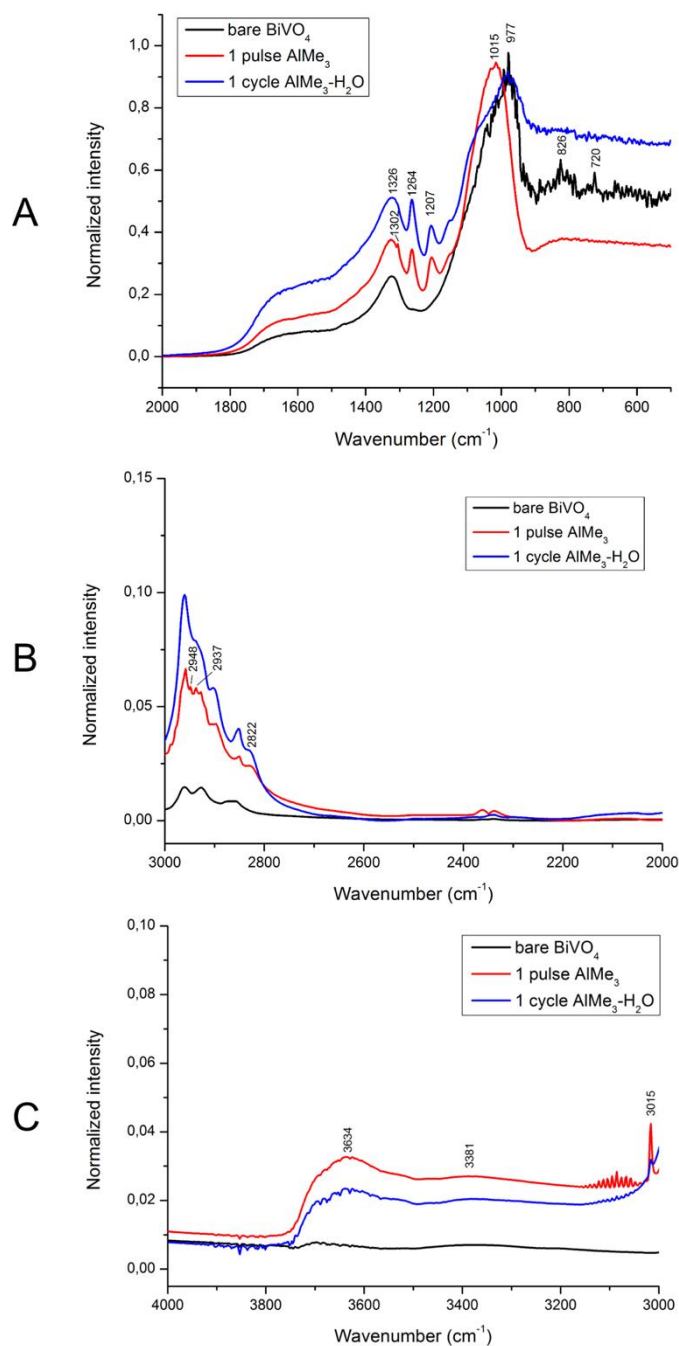


Figure 3. FTIR Spectra of dehydroxylated bare BiVO_4 powder, BiVO_4 powder with 1 pulse of AlMe_3 and 1 cycle $\text{AlMe}_3\text{-H}_2\text{O}$ at (A) $2000\text{-}500\text{ cm}^{-1}$ wavenumbers, (B) $3000\text{-}2000\text{ cm}^{-1}$ wavenumber, (C) $4000\text{-}3000\text{ cm}^{-1}$ wavenumber

Figure 3 shows the IR spectra of (i) vacuum pre-treated pristine BiVO_4 , (ii) BiVO_4 powder with 1 pulse of AlMe_3 , and (iii) after reaction with H_2O . The starting bare BiVO_4 , i.e., before the 1st pulse of AlMe_3 , is characterized by peaks at 720 cm^{-1} , 826 cm^{-1} , and 977 cm^{-1} which correspond to V-O wagging, symmetric, and asymmetric vibrations, respectively [31]. Peaks associated with O-H stretching vibrations are expected in 3374 cm^{-1} and 3700 cm^{-1} wavenumbers, although for the case of BiVO_4 it is not readily seen in the IR spectra.

Upon addition of the first pulse of AlMe_3 , the presence of the AlCH_3^* surface species was confirmed by the presence of the diagnostic $\nu(\text{C-H})$ stretching vibrations seen at $2822\text{-}2948\text{ cm}^{-1}$. The 3015 , 1207 , 1015 , 1264 and 1302 cm^{-1} peaks are yet unassigned. The subsequent H_2O pulse resulted to a broad O-H band at 3400 cm^{-1} in agreement with expected AlOH^* stretching vibrations from AlOH^* surface species in the

3600 cm⁻¹ region. The contribution to this band from OH vibration mode of physisorbed water molecules should be limited, due to the vacuum treatment step undergone by the sample between the water addition and the IR analysis.

Upon water addition on the Al-Me terminated surface (see reaction B above), the volatiles were condensed, analyzed and quantified by gas chromatography. In agreement with reaction B, methane was detected in the gas phase. The quantification of methane translated to 1.2 CH₄ evolved per reactive group titrated on the initial surface. This result is in the correct order of magnitude for the simplified growth mechanism proposed for ALD cycles to alumina and is also compatible with the possible formation of dipodal surface species [(-O)₂AlMe].

3.3 BiVO₄ thin-film electrode

The chemical composition of the BiVO₄ thin film electrodes was determined by XRD, XPS, FESEM-EDS and Raman analyses.

The high resolution XPS spectra for Bi4f, V2p, and O1s binding energy regions are shown in Figure 4. In agreement with the XRD data (see section 3.1), the thin-film photoelectrodes manifest the spin-orbit splitting for both the Bi4f_{7/2} and Bi4f_{5/2}, and the V2p_{3/2} and V2p_{1/2}, that are in good agreement with those reported in literature for monoclinic-scheelite structure of BiVO₄ [32]. Also, it is noteworthy that the Bi4f_{7/2} and Bi4f_{5/2} peaks appear in the binding energy region (158.5 eV and 163.8 eV, respectively) that is much higher than that of metallic Bi, i.e. 156.8 eV and 162.2 eV [32], respectively. These Bi4f peaks indicate the presence of Bi occurring mainly as Bi³⁺ species in the surface of the electrodes. Meanwhile, the V2p_{3/2} and V2p_{1/2} peaks at 516.1 eV and 523.7 eV, respectively, are characteristic of V occurring mainly as V⁴⁺ species on the surface of the photoanode. This is different from the bulk V species, which have a +5 oxidation state, as implied by EDS measurements and by earlier studies by us with depth profile XPS measurements [22]. The reduction of V⁵⁺ to V⁴⁺ on the surface of the BiVO₄ electrode induces oxygen vacancies that directly impact the electronic structure of the monoclinic scheelite BiVO₄. In fact, these oxygen vacancies have been observed from the O 1s spectra, the deconvolution of which yielded lattice oxygen at 529.2 eV, non-lattice oxygen at 530.3 eV, and chemisorbed or dissociated oxygen from water molecules at 532.0 eV [32–36]. The non-lattice oxygen refers to oxygen-deficient regions which might be populated with OH groups in order to correct the charge balance.

Furthermore, surface Bi/V atomic ratios revealed a Bi-rich surface for the BiVO₄ electrode before PEC tests (Bi/V: 2.3), while EDS measurements show a Bi/V ratio of 1 in the bulk. The Bi-rich surface of the BiVO₄ is a consequence of the segregation phenomena that has been observed for Bi-containing oxides, wherein the oxygen segregates to the surface, depleting the subsurface of oxygen, and leading to Bi-O surface terminations [37].

Upon Al-overlayer deposition, XPS investigation was also performed, and the spectra are shown in Figure S6. As expected, Al peak is clearly seen for the BiVO₄ sample that is modified with Al-overlayer deposition, whereas none can be observed for the bare BiVO₄. No change is observed for the V 2p peaks upon Al-overlayer deposition, but additional peaks at higher binding energies can be observed in the Bi 4f spectra. These are assigned to Bi⁵⁺, as also reported in the literature [38][39]. This shows that the Al-overlayer deposition slightly oxidize the surface of the BiVO₄.

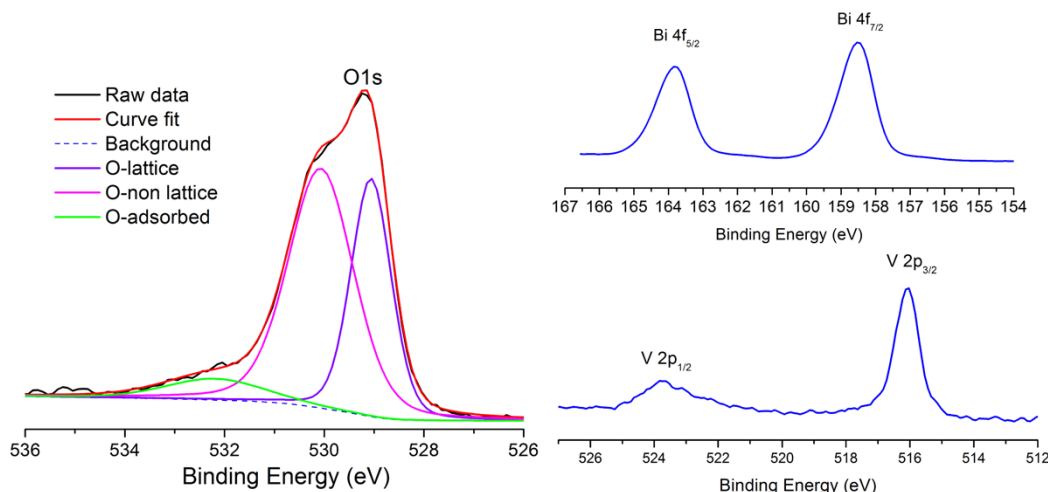


Figure 4. O1s, Bi 4f and V2p XPS spectra for bare BiVO₄ electrode

As a representative of the Al-modified samples, in Figure 5A is shown a low magnification FESEM image with an EDS map of Al, Bi, V and O elements in the BiVO₄ thin-film with 2 cycles of Al overlayer, which demonstrate an uniform coverage of FTO/glass substrate with the BiVO₄ film and an homogeneous deposition of Al on it, even at a low number of deposition cycles. Other elements (i.e. Si and Sn, not shown) were also visible in the EDS analyses due to the FTO/glass substrate. As shown in Figure 5B and C, the nanostructured porous morphology of the BiVO₄ particles remains unmodified and, as found in the bare BiVO₄, a Bi/V ratio of 1 was also observed in the Al-modified samples, confirming the no modification of the chemical composition of BiVO₄ after the Al deposition process.

The Raman spectra of bare and Al-modified BiVO₄ thin film electrodes are shown in Figure 6A. The most intense band at 822 cm⁻¹ is assigned to the V-O stretching mode and the weak shoulder at 709 cm⁻¹ is assigned to antisymmetric V-O stretching. The bands at 375 cm⁻¹ and 335 cm⁻¹ correspond to the symmetric and antisymmetric bending of VO₄ tetrahedra. There was a slight difference observed at the 201-214 cm⁻¹ bands, but these are ascribed to the external mode of BiVO₄, which is not exactly structural in nature [40]. Therefore, based on the Raman spectra, it can be also confirmed that the Al overlayer did not induce structural modifications on the BiVO₄. This result is also supported by the UV-Vis absorption analysis shown in Figure S3 in the SI. Only minor differences are observed in the absorption spectra of all the bare BiVO₄ and Al-modified BiVO₄ samples (Figure S3A), which is within the sample-to-sample variation. From these absorption spectra, Tauc analyses were performed in order to determine the bandgaps. Tauc plots for direct and indirect bandgap analyses are shown in Figure S3B and C, respectively, where only very little changes of bandgaps are observed (2.48 and 2.41 ± 0.01 eV, respectively). Overall, as expected, the Al overlayer does not affect the bulk structural and optical properties of BiVO₄.

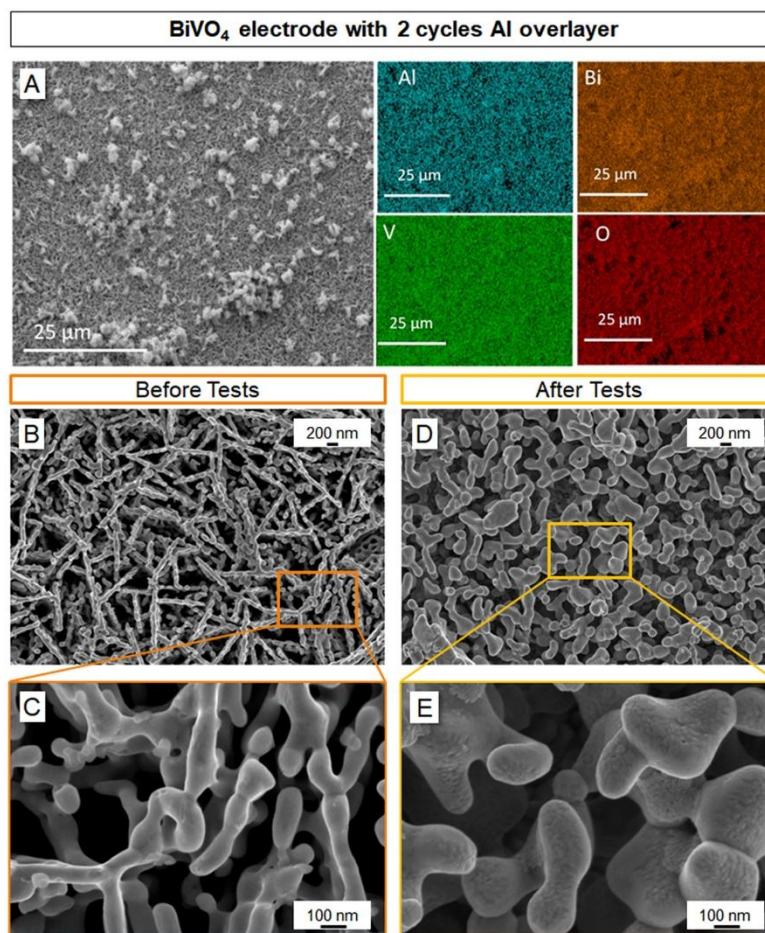


Figure 5. FESEM-EDS analyses of Al-modified BiVO₄ electrode made by 2 cycles: Low magnification FESEM image and EDS maps of Al, Bi, V and O elements on the fresh electrode (A); FESEM images before (B, C) and after (D, E) photo-electrochemical water oxidation tests in 0.1M NaPi buffer.

The effect of varying the number of cycles in the ALD-like deposition method on the photoactivity of the BiVO₄ thin film electrodes was investigated. Figure 6B and C shows the linear sweep voltammetry and chronoamperometry curves under chopped light conditions for all the samples modified with Al, as compared with that of the bare BiVO₄ thin film electrode. Indeed, for very few pulses of AlMe₃-H₂O cycles, the formation of alumina oxide cannot be inferred. All curves manifested the initial current spikes appearing readily when the light source was turned on, which eventually dampened, which suggests the occurrence of fast electron-hole recombination. For the bare BiVO₄ sample, a photocurrent density of 0.35 mA/cm² at 1.23 V vs RHE was achieved. It can be clearly seen from the same figure that an improvement in photocurrent density values was achieved with 2 cycles and 5 cycles of Al deposition, yielding 0.54 mA/cm² and 0.49 mA/cm² at 1.23 V vs RHE, respectively, in the LSV curves. Under CA tests at 1.23 V vs RHE, the photocurrents of these two samples stabilized at a bit lower and similar value of 0.38 mA/cm². However, lower photocurrent density was observed when the number of Al-deposition cycles was increased to 8. The influence of Al-deposition cycles to the incident photon-to-current conversion efficiency (IPCE) was also investigated and the resulting curves for the different samples under back-side illumination are shown in Figure 6D. The IPCE increases from the bare BiVO₄ sample to that with 2 cycles Al deposition, and it decreases again for higher number of Al deposition cycles. The differences between samples are rather larger than those observed from the LSV curves. The reason for this may be related to the instability of the films, which will be discussed later in the manuscript. Nevertheless, the overall trend qualitatively agrees with the LSV and CA measurements.

It is noteworthy that the reaction temperature used in the ALD-like deposition of the Al overlayer on the BiVO₄ surface, which yielded the better performance is low enough at 60°C, which is not commonly demonstrated in typical ALD processes involving Al₂O₃, commonly performed at 125-500°C [30].

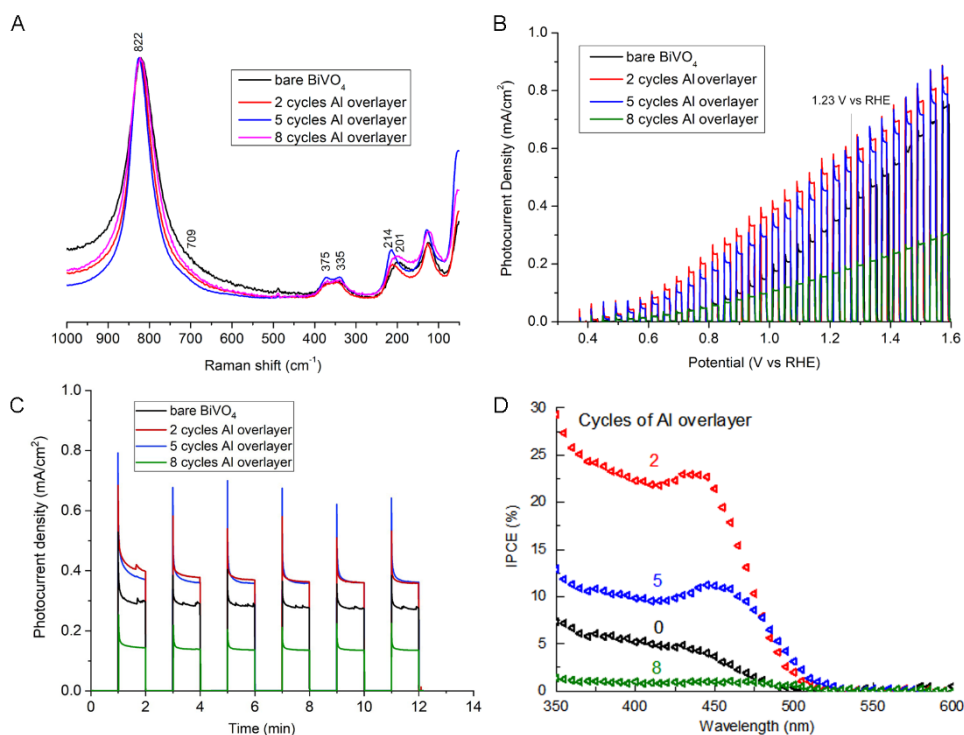


Figure 6. (A) Raman spectra of bare and Al-modified BiVO₄ electrodes. PEC water oxidation tests of bare and Al-modified BiVO₄: (B) LSV plots under chopped light (scan rate: 10 mV/s), (C) chronoamperometries under chopped light, (D) IPCE spectra and (D) Raman spectra. Tests were made with 0.1 M Na-Pi buffer pH 7.

To confirm that the higher photocurrent values of the Al-modified BiVO₄ electrodes are mainly due to water oxidation, we measured the O₂ generated by the highest performing Al-modified samples (i.e. with 2 cycles) using differential electrochemical mass spectrometry (DEMS) (see experimental section for measurement details). Figure 7A shows a linear sweep voltammetry curve, directly compared with the O₂ signal simultaneously measured with DEMS. Both curves correspond well with each other, suggesting that the O₂ generation can be correlated with the photocurrent. Indeed, by using the same system but under chronoamperometry condition, the Faradaic efficiency for O₂ evolution was determined to be 100.0 ± 0.6 % at 1.0 V vs. RHE. All photocurrents can therefore be attributed to the water oxidation reaction.

In order to verify if the Al overlayer is indeed passivating the surface states in the BiVO₄ electrode surface, rapid scan voltammetry was performed to determine the surface capacitance of the electrodes. As shown in Figure 7B, the surface capacitance decreases by orders of magnitude with increasing number of cycles of Al, in agreement with passivating surface states that serve as charge recombination sites. This is important because the photocurrent of BiVO₄ has been reported to be limited more by surface recombination than the charge transfer [41].

Meanwhile, the Nyquist impedance plot is shown in Figure 7C. The charge transfer resistance, which was indicated by the diameter of the arc, is seen to be highest for the 8 cycles Al electrode (green arc), and greater than that of bare BiVO₄ (black arc). This is consistent with the trend observed for the photocurrent density, where it was seen that the bare BiVO₄ performed better than the 8 cycles Al overlayer. Therefore, the thickest layer of Al overlayer contributed in slowing down the transfer of holes on the BiVO₄-electrolyte interface. Also, it can be seen from Figure 7C, that the 2 cycles Al overlayer (red arc) and the 5 cycles Al overlayer (blue arc) have lower charge transfer resistances than the bare BiVO₄, thus, both having higher photocurrent density relative to the bare BiVO₄. However, between these 2 electrodes, it turned out that the 5 cycles Al has a lower charge transfer resistance than the 2 cycles Al, which was the opposite behaviour of the observed photocurrent density. It appears that the higher photocurrent density of the 2 cycles Al electrode is explained by the donor densities as derived from the Mott-Schottky plots (shown in Figure S4 in the SI),

wherein the 2 cycles Al electrode manifested a donor density of $1.49 \times 10^{20} \text{ cm}^{-3}$, while the 5 cycles Al electrode has a lower donor density of $1.16 \times 10^{20} \text{ cm}^{-3}$. A higher donor density can improve the PEC response by raising the Fermi level, which creates more band bending that enhances electric field in the space charge layer, thus, lowering the electron-hole recombination. Second, it enhances the electrical conductivity of the photoanode, thus, improving the charge transport properties within the material. Moreover, the onset potentials of these electrodes were almost equal at 0.39 V, 0.37 V, 0.38 V, and 0.37 V vs RHE, for bare BiVO₄, 2 cycles Al, 5 cycles Al, and 8 cycles Al, respectively.

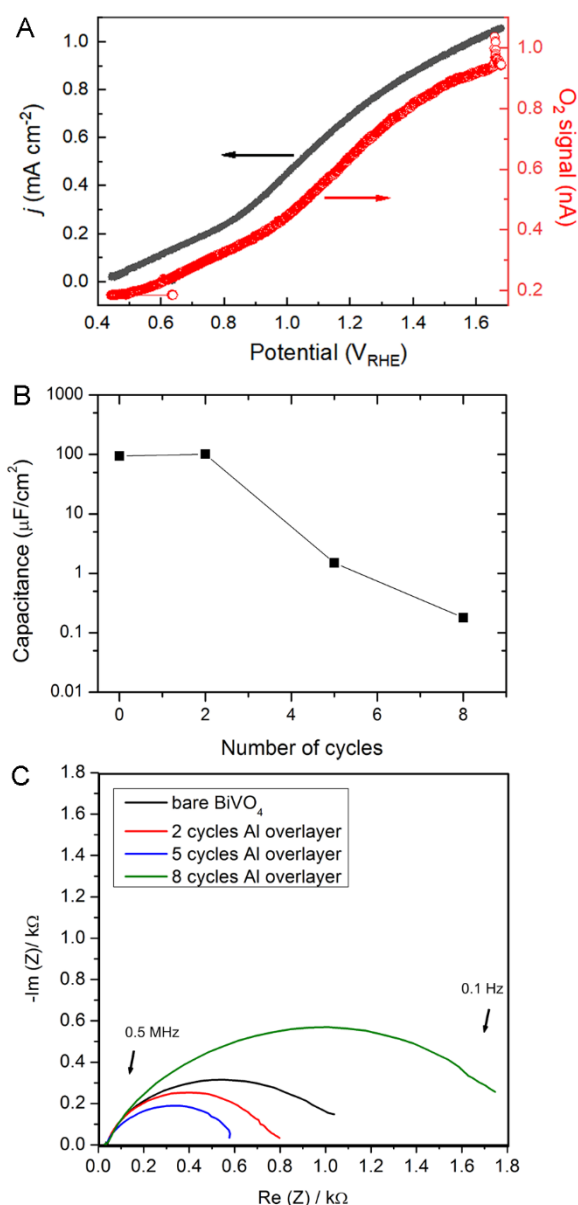


Figure 7. (A) Measurement of O₂ signal detected simultaneously during linear sweep voltammetry on 2 cycles Al-modified electrode. (B) Surface capacitance and (C) Nyquist impedance plots for bare and Al-modified BiVO₄.

The 2 cycles Al electrode, which exhibited the best photocurrent density, was subjected to a stability test along with the bare BiVO₄ electrode. The result of the stability test is shown in Figure 8. The bare BiVO₄ (black line) showed an 85% decay in photocurrent density after 7.5 hours, while the 2 cycles Al (blue line) electrode showed 59.6% decay. To understand the reason of such decay in the performance, post-reaction FESEM-EDS and XPS analyses were performed. Figure 5D and E show the FESEM images of the 2 cycles Al modified sample after testing. An increase of the BiVO₄ particles size and rearrangement of the porous structure of the film after the PEC test are observed. The same behavior was also noticed in the bare BiVO₄

film (see Figure S5, SI); however, uncoated regions of the FTO substrate clearly appeared after the 7.5 h of operation in the bare BiVO₄ film (see Figure S5E, SI), while the Al-modified film was already preserved from this point of view. From EDS analyses it was observed a Bi-enrichment of the films: the Bi/V ratio increased from 1.0 to 1.2 and 1.1, in the bare BiVO₄ and the 2 cycles Al-modified electrode, respectively, which can be explained by the dissolution of V atoms from the BiVO₄ surface during the PEC tests [42]. Indeed, the Bi/V ratio from XPS analysis for the bare BiVO₄ slightly increases from 2.3 (vide supra) to 2.8 after PEC measurement. In addition, Bi atoms on the surface of the bare BiVO₄ sample become partially oxidized to Bi⁵⁺ ([Bi⁵⁺] increased from 0 to ~20%, see Figure S7A), indicating that the photocurrent decay may be related to an oxidative photo-corrosion process. In contrast, although the Bi atoms are already partially oxidized to begin with in the 2 cycles Al-modified sample, PEC measurement only slightly oxidize the surface further ([Bi⁵⁺] slightly increased from 23 to 29%, see Figure S7B). Instead, the instability observed in the Al-modified BiVO₄ may be related to the detachment of Al, as observed from disappearance of peak in the Al 2p core level spectra (see Figure S7C). Further investigation on better adhesion of Al on the BiVO₄ surface is therefore needed in order to extend the stability.

Overall, although the stability of the BiVO₄ photoanode clearly remains an issue, it was demonstrated here that the presence of an Al overlayer on the BiVO₄ surface arrested some of the photo-corrosion and reduced the photocurrent decay by at least 15%.

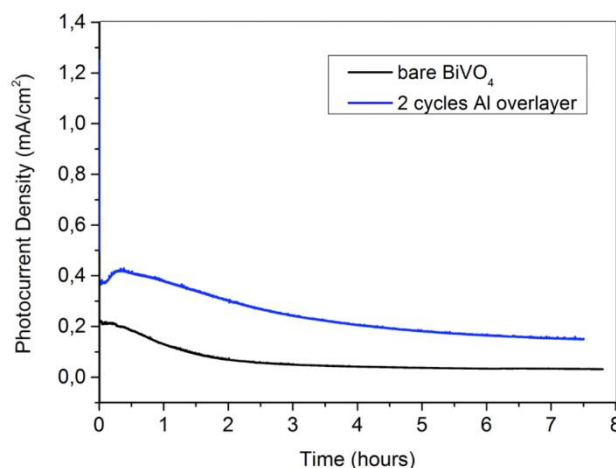


Figure 8. Stability test (chronoamperometry) plot for 2 cycles Al and bare BiVO₄

4 Conclusion

In order to minimize the inefficiencies due to electron-hole recombination and passivate the surface states, ultrathin Al oxo/hydroxyls overlayers were deposited onto the BiVO₄ thin film electrodes in an ALD-like manner (alternating pulses of trimethyl aluminum and water). This was also performed in order to protect the BiVO₄ surface from photocorrosion and increase its stability. A photocurrent density of 0.54 mA/cm² at 1.23 V vs RHE was obtained for the 2 cycles Al overlayer - BiVO₄ electrode, which was a 54% improvement from the bare BiVO₄ that demonstrated a photocurrent density of 0.35 mA/cm² at 1.23 V vs RHE. A 15% increase in stability of the 2 cycles Al overlayer- BiVO₄ electrode was also observed over 7.5 hours of continuous irradiation. Finally, through surface capacitance measurements, it was shown that the Al overlayer was indeed passivating the surface states of the BiVO₄ electrodes.

Chemical insight into the nature of the Al-modified BiVO₄ surface was also gained by studying the larger surface area BiVO₄ powder, used as a model of the photoanode. Chemical titration of the BiVO₄ powder with n-BuLi led to the evolution of butane (1.5 molecule/nm² of BiVO₄ surface), thus highlighting the existence of surface reactive groups on BiVO₄, whose chemical nature has not yet been defined. If the presence of surface hydroxyls, postulated elsewhere in the literature, is confirmed, this work suggests a maximum of 1.5 of such reactive site/nm² on BiVO₄. Such surface site reacts with AlMe₃ to yield surface

alkyls, which can be hydrolyzed by a further pulse of water and concomitant methane release (1.2 CH₄ molecules released by the reactive group of the initial surface). This work on model powder BiVO₄ confirms that chemically reasonably well-behaved ALD-like half-cycles of AlMe₃ and H₂O can be alternated on BiVO₄ surfaces, thus providing a molecular model for the useful chemical modification reported herein for the thin film BiVO₄ photoanodes.

Acknowledgments

The authors thank the EACEA Erasmus+ SINCHEM Grant FPA 2013-0037 for the financial support. Part of the work described in this paper has been conducted within the project SUNCOCHEM. This project has received funding from the European Union's Horizon 2020 Innovation Action programme under the Grant Agreement No 862192. From Politecnico di Torino, we acknowledge Mauro Raimondo for the FESEM measurements and Enrico Sartoretti for the assistance in Raman spectra interpretation. The support of CNRS, Université de Lyon 1 and CPE Lyon Sustainable chair is also gratefully acknowledged.

References

- [1] Z. Chen, H.N. Dinh, E. Miller, Photoelectrochemical Water Splitting Standards, Experimental Methods, and Protocols, 2013.
- [2] M.G. Walter, E.L. Warren, J.R. McKone, S.W. Boettcher, Q. Mi, E.A. Santori, N.S. Lewis, Chem. Rev. (Washington, DC, United States) 110 (2010) 6446–6473.
- [3] J.K. Hurst, Science (80-.). 328 (2010) 315–316.
- [4] M. Grätzel, J. Moser, 5 (2001) 589–644.
- [5] A. Harriman, I.J. Pickering, J.M. Thomas, P.A. Christensen, J. Chem. Soc. Faraday Trans. 1 84 (1988) 2795–2806.
- [6] J. Kiwi, M. Grätzel, Nature 281 (1979) 657–658.
- [7] A. Kudo, Keiko Omori, H. Kato, (1999) 11459–11467.
- [8] Y. Park, K.J. McDonald, K.-S. Choi, Chem. Soc. Rev. (2013) 2321–2337.
- [9] T.W. Kim, Y. Ping, G.A. Galli, K.-S. Choi, Nat. Commun. 6 (2015) 8769.
- [10] A. Kudo, K. Ueda, H. Kato, I. Mikami, Catal. Letters 53 (1998) 229–230.
- [11] D.J. Payne, M.D.M. Robinson, R.G. Egdell, A. Walsh, J. McNulty, K.E. Smith, L.F.J. Piper, Appl. Phys. Lett. 98 (2011) 46–49.
- [12] S. Hu, C. Xiang, S. Haussener, A.D. Berger, N.S. Lewis, Energy Environ. Sci. 6 (2013) 2984–2993.
- [13] F.F. Abdi, N. Firet, R. vandeKrol, ChemCatChem 5 (2013) 490–496.
- [14] R.S. Bonilla, B. Hoex, P. Hamer, P.R. Wilshaw, Phys. Status Solidi A 214 (2017).
- [15] L. Steier, I. Herraiz-cardona, S. Gimenez, F. Fabregat-santiago, J. Bisquert, S.D. Tilley, M. Grätzel, (2014).
- [16] R. van de Krol, M. Grätzel, Photoelectrochemical Hydrogen Production, 2012.
- [17] K. Tolod, S. Hernández, N. Russo, Catalysts 7 (2017) 13.
- [18] E.O. Filatova, A.S. Konashuk, J. Phys. Chem. C 119 (2015) 20755–20761.
- [19] G. Dingemans, W. Beyer, M.C.M. Van De Sanden, W.M.M. Kessels, 152106 (2012) 1–4.
- [20] G. Chang, D.W.Y. Zhang, A. Aldalbahi, Nucl. Sci. Tech. (2016) 2–7.
- [21] S.M. Thalluri, C. Martinez Suarez, S. Hernández, S. Bensaid, G. Saracco, N. Russo, Chem. Eng. J. 245 (2014) 124–132.
- [22] K.R. Tolod, S. Hernández, M. Castellino, F.A. Deorsola, E. Davarpanah, N. Russo, Int. J. Hydrogen Energy 45 (2020) 605–618.
- [23] F. Wang, W. Septina, A. Chemseddine, F.F. Abdi, D. Friedrich, P. Bogdanoff, R. Van De Krol, S.D. Tilley, S.P. Berglund, J. Am. Chem. Soc. 139 (2017) 15094–15103.
- [24] R. Irani, P. Plate, C. Höhn, P. Bogdanoff, M. Wollgarten, K. Höflich, R. Van De Krol, F.F. Abdi, J. Mater. Chem. A 8 (2020) 5508–5516.
- [25] A. Bhattacharya, K. Mallick, A. Hartridge, Mater. Lett. 30 (1997) 7–13.
- [26] C. Martinez Suarez, S. Hernández, N. Russo, Appl. Catal. A Gen. 504 (2015) 158–170.
- [27] C. Copéret, A. Comas-Vives, M.P. Conley, D.P. Estes, A. Fedorov, V. Mougél, H. Nagae, F. Nunez-Zarur, P.A. Zhizhko, Chem. Rev. 116 (2016) 323–421.
- [28] D.E. Starr, M. Favaro, F.F. Abdi, H. Bluhm, E.J. Crumlin, R. van de Krol, J. Electron Spectros. Relat. Phenomena (2017).

- [29] S. Cadot, O. Renault, M. Frégnaux, D. Rouchon, E. Nolot, K. Szeto, C. Thieuleux, L. Veyre, H. Okuno, F. Martin, E.A. Quadrelli, *Nanoscale* 9 (2017) 538–546.
- [30] M.D. Groner, F.H. Fabreguette, J.W. Elam, S.M. George, (2004) 639–645.
- [31] Z. Zhao, Z. Li, Z. Zou, *RSC Adv.* 1 (2011) 874–883.
- [32] L.H. Dall’Antonia, N.R. de Tacconi, W. Chanmanee, H. Timmaji, N. Myung, K. Rajeshwar, *Electrochem. Solid-State Lett.* 13 (2010) D29.
- [33] S. Wang, P. Chen, Y. Bai, J.H. Yun, G. Liu, L. Wang, *Adv. Mater.* 30 (2018) 1–7.
- [34] J. Wu, Y. Chen, L. Pan, P. Wang, Y. Cui, D. Kong, L. Wang, X. Zhang, J. Zou, *Appl. Catal. B Environ.* 221 (2018) 187–195.
- [35] S. Bai, Q. Li, J. Han, X. Yang, X. Shu, J. Sun, L. Sun, R. Luo, D. Li, A. Chen, *Int. J. Hydrogen Energy* 44 (2019) 24642–24652.
- [36] H. Bai, P. Guan, K. Qu, W. Fan, F. Wang, D. Xu, J. Ding, W. Shi, *Int. J. Hydrogen Energy* 44 (2019) 28184–28193.
- [37] D. Passerone, R. Erni, (2015).
- [38] R.P. Antony, T. Baikie, S.Y. Chiam, Y. Ren, R.R. Prabhakar, S.K. Batabyal, S.C.J. Loo, J. Barber, L.H. Wong, *Appl. Catal. A Gen.* 526 (2016) 21–27.
- [39] G. Zhang, L. Cai, Y. Zhang, Y. Wei, *Chem. – A Eur. J.* 24 (2018) 7434–7444.
- [40] B.J. Yu, A. Kudo, (2006) 2163–2169.
- [41] C. Zachäus, F.F. Abdi, L.M. Peter, R. Van De Krol, *Chem. Sci.* 8 (2017) 3712–3719.
- [42] K. Sayama, A. Nomura, T. Arai, T. Sugita, R. Abe, T. Oi, Y. Iwasaki, Y. Abe, H. Sugihara, *J. Phys. Chem. B* 3 (2006) 11352–11360.